

Structural compliance, misfit strain and stripe nanostructures in cuprate superconductors

S. J. L. Billinge and P. M. Duxbury

*Department of Physics and Astronomy and Center for Fundamental Materials Research,
Michigan State University, East Lansing, MI 48824-1116.*

(February 1, 2008)

Structural compliance is the ability of a crystal structure to accommodate variations in local atomic bond-lengths *without incurring large strain energies*. We show that the structural compliance of cuprates is relatively small, so that short, highly doped, Cu-O-Cu bonds in stripes are subject to a *tensile misfit strain*. We develop a model to describe the effect of misfit strain on charge ordering in the copper oxygen planes of oxide materials and illustrate some of the low energy stripe nanostructures that can result.

74.72.Dn, 74.72.-h, 74.80.-q, 61.72.Lk

The existence of charge stripes in high T_c superconductors [1] and their relevance to the high- T_c property [2,3] are hotly debated subjects at present. The tendency towards charge phase separation and stripe formation has been seen in models of strongly correlated electron systems [2–6]. Charge stripes have also been seen directly in strongly correlated systems such as manganites [7] and nickelates [8]. In the cuprates, convincing direct evidence for stripes comes with the observation of charge-order superlattice peaks in $\text{La}_{1.6-x}\text{Nd}_{0.4}\text{Sr}_x\text{CuO}_4$, though the observation of static long-range ordered stripes correlates with poor or nonexistent superconductivity [1,9]. The interest has shifted to dynamic fluctuating short-range ordered stripes. Indirect experimental evidence exists from inelastic neutron scattering supporting their presence in $\text{La}_{2-x}(\text{Sr},\text{Ba})_x\text{CuO}_4$ [10] and $\text{YBa}_2\text{Cu}_3\text{O}_{6+\delta}$ [11,12]. The observation of a pseudo gap in the electronic density of states above T_c is even more widespread [13] and can be interpreted as originating from dynamic stripes. Of critical importance is an understanding of what prevents stripes ordering over long-range and becoming static and insulating. Here we stress the importance of lattice strain to this phenomenon.

Strong coupling of doped charges to the lattice is clearly evident in the cuprates [1,11,14,15]. A direct way in which the charge couples to the lattice is through the Cu-O bond length which depends on charge filling of the Cu-O σ^* covalent bond [16]. Doping holes into the CuO_2 plane reduces charge density in this bond which stabilizes and shortens the bond. This is seen experimentally as a shortening of the Cu-O bond with increasing doping [17] and has profound implications when charge-stripes are present. The presence of charge stripes implies that regions of the CuO_2 plane that are heavily doped, and therefore have short bonds, coexist with undoped regions with long bonds. Experimental evidence for this coexistence has been presented in superconducting $\text{La}_{2-x}(\text{Sr},\text{Ba})_x\text{CuO}_4$ samples [18]. We show that this results in a misfit strain that breaks up the stripes into a domain microstructure. The characteristic length-scale of the domains depends on the misfit strain and can range

from nanometer to long range. The importance of elastic compliance and interface strain to texture formation has been discussed in related ferroelastic materials [19] but this is the first time it is discussed in the context of breaking up stripes and forming stripe nanostructures.

A key property of perovskite structures is their capacity to accommodate atoms of various sizes. They do this via a variety of buckling and tilt modes. These modes have relatively small strain energy costs, and are frequently called soft or floppy modes [16,20,21]. In manganites, nickelates and cuprates, the key soft mode is a buckle in the Cu-O-Cu bond and doping typically relaxes this buckle in these materials. This low energy accommodation affects the stability of the structure against polaron formation [22]. We argue that in cuprates, the short Cu-O-Cu bond is not fully accommodated by relaxation of the buckle present in the undoped copper-oxygen bond. This leads to tensile misfit strains in the copper oxygen planes of cuprates. In the presence of stripes the tensile misfit strains can lead to a variety of domain microstructures. We develop a model to describe these microstructures and present some illustrative results using the model.

The ability of the structure to accommodate local bond shortening we call “structural compliance” δ_s . Where this accommodation comes from octahedral tilting it is defined as $\delta_s = \frac{(r_b - r_f)}{r_b} = (1 - \cos \alpha)$ where r_b and r_f are the lengths of the Cu-O bond in the “buckled” and “flat” configurations respectively and α is the angle the Cu-O bond makes with the plane (Fig. 1). In the reduced $I4/mmm$ unit cell of the $\text{La}_{2-x}(\text{Sr},\text{Ba})_x\text{CuO}_4$ system r_f is simply $a/2$ where a is the lattice parameter. In general α is small and $\delta_s \approx \alpha^2/2$. The structural compliance therefore depends very sensitively on the buckling angle. In the case of low-temperature orthorhombic (LTO) [17], and tetragonal (LTT) [23], octahedral tilts observed in $\text{La}_{2-x}(\text{Sr},\text{Ba})_x\text{CuO}_4$, $\alpha = \theta_{LTT} = \theta_{LTO}/\sqrt{2}$ where θ_{LTT} and θ_{LTO} are the octahedral tilt angles in the LTT and LTO phases respectively. We note that for the same tilt angle the LTT symmetry tilts have twice the structural

compliance.

However the $\text{La}_{2-x}(\text{Sr,Ba})_x\text{CuO}_4$ system has a relatively small structural compliance, as do the other high T_c cuprates. On going from undoped to heavily doped ($x = 0.20$) in the $\text{La}_{2-x}(\text{Sr,Ba})_x\text{CuO}_4$ system at 10K, the Cu-O bond shortens from $r_b = 1.904 \text{ \AA}$ to $r_b = 1.882 \text{ \AA}$, i.e., by $\sim 0.022 \text{ \AA}$ [17]. For illustration purposes, we take this bond length difference to be an estimate of the difference in length of the short and long Cu-O bonds in the Cu-O planes. In order for structural compliance to accommodate this bond length mismatch we need $\delta_s = 0.022/1.89 = 0.012$, which requires a tilt angle of 8.9° in the LTT symmetry and of 12.6° in the LTO system. However in the $\text{La}_{2-x}(\text{Sr,Ba})_x\text{CuO}_4$ system tilts have LTO symmetry with a tilt angle of $\sim 3.5^\circ$ resulting in a structural compliance of only $\delta_s \sim 0.001$. There is therefore insufficient structural compliance to accommodate the short Cu-O bonds in these materials, resulting in a misfit strain if charges localize, for example, in stripes. Note that these numbers represent rough estimates and the precise value for the crossover will depend on the charge density and degree of delocalization of the charge in the stripe as well as details of whether the stripes are site or bond centered. Nevertheless, it is evident that in cuprates, stripe formation will lead to misfit strain, but that materials with moderate tilts could accommodate short bonds with little or no misfit strain.

We now consider what happens to the microstructure of the charge stripes in the case where a misfit strain is present. We expect/show that the presence of strain results in a break-up of the stripes into short segments. Lattice strain therefore prevents the stripes from ordering over long range; a situation that is a prerequisite for most stripe theories of high temperature superconductivity [2,3,24–28]. This has implications for superconductivity by producing an electronic microstructure [29] of domains of broken stripes that results in a high density of topological stripe defects [25,30,31]. The ends of the stripes are in a state of high stress making them especially susceptible to charge fluctuations.

We assume that neighboring doped Cu sites in a stripe have a separation, l_0 that is shorter than, but approximately equal to, the average separation, a , dictated by the crystal structure and the average doping level. In this case, as the stripes form and increase in length strain energy will build up. The basic competition is between the length scale of the periodic potential a due to the lattice structure and the natural length of the short bonds due to near neighbor doped sites, as illustrated in Fig. 2. The breakup length scale of the stripes is approximated by comparing the strain energy gain ($\sim k_{nn}N(a-l_0)^2/2$) which occurs when a strained stripe of length $L = Na$ breaks up, to the formation energy per bond of an unstrained stripe ($-J_{nn}$). This yields (dropping constant prefactors)

$$N_c \approx \left(\frac{J_{nn}}{k_{nn}}\right)\left(\frac{1}{a-l_0}\right)^2. \quad (1)$$

The key parameters setting the scale of the energies in Eq. (1) are k_{nn} , which is proportional to the stiffness of the Cu-O bonds and J_{nn} the energy gain (per bond) in forming stripes. The spring constant $k_{nn} \sim V_0/a^2$, where V_0 is of the order of an ionic bond energy ($\sim 5 \text{ eV}$). J_{nn} is of the order of the stripe formation temperature, e.g., the temperature where the pseudogap appears $\sim 400\text{K} \sim 40\text{meV}$. As discussed above, the misfit strain for cuprates is of order $(a-l_0)/a \sim 0.01$. Using these numbers in Eq. (1) indicates that for cuprates, the characteristic length of stripe domains, N_c , should be of order 100 lattice spacings. The stripe length diverges quadratically (see Eq. (1)) as the misfit strain approaches zero leading to long range stripes in oxides with no misfit strain, as appears to be the case, for example, in $\text{La}_{2-x-y}\text{Nd}_y\text{Sr}_x\text{CuO}_4$.

We now develop a model to test whether the simple prediction (1) holds when there are many stripes and to study the stripe nanostructures produced once strain destabilizes long-range stripes. This model is as simple as possible while including the key aspects of doping, stripes and misfit strain. Note that this model considers only *stripe breakup* and not stripe formation. We assume magnetic effects and long-range Coulomb interactions play a key role in stripe formation [6,32,33], but that misfit strain leads to their breakup. Quantum fluctuations may also contribute to stripe breakup, however we consider here only misfit strain which we assume is the dominant factor. The model is defined on a square lattice where each site is assigned an occupancy number n_i where $n_i = 1$ indicates that the site is doped with a hole and $n_i = 0$ indicates that it is undoped.

$$H = -\sum_{ij}^{nn} J_{nn}n_in_j + \sum_{ij}^{nnn} J_{nnn}n_in_j + \mu\sum_i n_i + \sum_{ij}^{nn} k_{nn}(l_{ij}-l_0)^2n_in_j + \sum_i n_i V(\vec{r}_i). \quad (2)$$

In the spirit of the stripes seen in $\text{La}_{1.6-x}\text{Nd}_{0.4}\text{Sr}_x\text{CuO}_4$ where a hole resides on every second site along the stripe, we can simplify the computation by considering a sublattice of every second Cu site and include an attractive nearest neighbor and repulsive next nearest neighbor interaction, J_{nn} and J_{nnn} respectively. These will result in stripe formation provided $J_{nn} > 0, J_{nnn} > 0$. The third term in the Hamiltonian has the chemical potential, μ , and allows us to vary the doping in the model to some occupation density, ρ . Note that our sublattice model only allows doping at every second copper site along the x and y directions so that ρ is related to the doping fraction p in the cuprates via, $\langle\rho\rangle \approx 4p$. The last two terms in Eq. (2) are the strain terms. The first term contains the misfit strain which occurs when two nearest neighbor sites on the sublattice are occupied (this corresponds to next-nearest neighbor sites in the cuprates). The parameter l_0 is the *natural length* of this bond, i.e., the length that bond would take in the absence of stress. The second term $V(\vec{r}_i)$ is the periodic potential imposed on the copper oxide layers by the crystal structure. In our model we take this potential to be modulated along both of the

in-plane axes of the CuO_2 planes with a wavelength a , and to have a amplitude V_0 . These terms in the Hamiltonian result in a finite stress energy unless $l_0 = a$ as can be seen in the schematic in Fig. 2. The strain energy is long range and has to be relaxed self consistently using a gradient or Newton's method.

It is difficult to find the ground state of the strained lattice gas (2), however it is easy to demonstrate that long range stripes are unstable in the presence of misfit strain and to test the general form (1). To illustrate this, consider the three stripe nanostructures of Fig. 3. From the lattice gas model (2), it is evident that the long range stripe has the lowest energy, provided there is no misfit strain. However in the presence of misfit strain, the lower two nanostructures of Fig. 3 have lower strain energy, though they do incur an energy cost proportional to J_{nn} due to breaking up the long range stripes. The strain energy in the long stripes is simply $k_{nn}(l_0 - a)^2/2$ per bond. For a strain of 0.01 and $V_0 = 1 = k_{nn}$ (in lattice units), this leads to a strain energy of 0.0152 for the structure of the top panel in Fig. 3. In contrast the interleaved stripe and weave structures (bottom two panels in Fig. 3) have strain energies of 0.0100 and 0.00765 respectively. These calculations were carried out using simple gradient descent on the unit cells of Fig. 3, with the periodic cell shape fixed, and the boundary atoms fixed and excluded from the total energy calculation. Tests using free and periodic boundaries and other nanostructures indicate that the state of lowest energy does depend on a variety of factors, including doping, boundary conditions and cell size. However in all cases, the strain energy of the long range stripes is of order twice that of the stripe domain states and this is not sensitive to the modeling details. It is thus reasonable to find the breakup length scale of the long range stripe array (top panel of Fig. 3) by comparing the strain energy of long-range stripes with the nearest neighbor energy cost incurred in breaking the stripes. This leads to $N_c k_{nn}(l_0 - a)^2 \approx J_{nn}$, which is consistent with the simple estimate (1). In general, the ground state structures of discrete strained systems are extremely rich [34–38] and we expect a similar richness in the ground structure of the Hamiltonian (2) as a function of doping and temperature, as will be described elsewhere. However the main point emphasized here is that misfit strain destabilizes long range stripes in cuprates at a length scale well approximated by (1).

Now we briefly comment on a number of experimental observations that can be explained by strain induced stripe nanostructures. The most important point is that the presence of strain will prevent the stripes from ordering over long range resulting in broken stripes even at moderately high dopings. Broken stripes will have significant quantum fluctuations. More structural compliance in the form of enlarged octahedral tilt distortions will reduce the misfit strain and cause the stripes to grow in length, presumably slowing their dynamics. Systems where the CuO_2 plane is in tension, or nearly in tension, such as the Hg and Tl systems will have faster stripe dy-

namics and therefore better superconducting properties and higher T_c 's as observed. Similarly, the increase in T_c with decreasing tilt distortions [39,40] have an explanation here. The strained stripes will also tend to stabilize the LTT phase over the LTO phase because this results in greater structural compliance, as we discussed, and therefore a decrease in the misfit strain. Stripe microstructures such as those shown in the third panel of Fig. 3 will result in *local* LTT symmetry tilts but averaging over the two 90° rotated LTT variants will lead to effective LTO behavior, as observed in $\text{La}_{2-x}\text{Ba}_x\text{CuO}_4$ [41]. Also, severely misfitting ions will give rise to large amplitude tilts locally, resulting in locally varying structural compliance, which will tend to pin the stripes. This explains the observation that superconductivity can be suppressed by increasing the mean-square dopant-ion size at fixed average dopant-ion size [42]. Finally, we note that ferroelastic effects [43] and the observation of tweed microstructures [19,35,44], as well as the sensitivity of T_c on dopant ordering in $\text{YBa}_2\text{Cu}_3\text{O}_{6+\delta}$ and $\text{La}_{2-x}\text{CuO}_{4+\delta}$, might have an explanation in strained stripe induced microstructures.

In summary, we point out that doping shortens the Cu-O bond length and that inhomogeneous doping in the form of stripes results in a tensile misfit strain. This breaks up the stripes and results in, presumably fluctuating, domains of broken stripes where the domain size depends on the misfit strain. Structural compliance in the form of buckling modes can reduce the misfit strain and result in long range ordered and static or quasi-static stripes reducing or destroying superconductivity.

SJLB thanks the National Science Foundation for support through grant DMR-0075149 and appreciates stimulating conversations with Emil Bozin, Takeshi Egami, Antonio Bianconi and Dragan Mihailovic. PMD thanks the Department of Energy for support through grant DE-FG02-90ER45418.

-
- [1] J. M. Tranquada et al., Nature **375**, 561 (1995).
 - [2] V. J. Emery et al., Proc. Natl. Acad. Sci. USA **96**, 8814 (1999).
 - [3] I. Martin et al., Europhys. Lett. **56**, 849 (2001)
 - [4] J. Zaanen and O. Gunnarson, Phys. Rev. B **40**, 7391 (1989).
 - [5] S. R. White and D. J. Scalapino, Phys. Rev. B **61**, 6320 (2000).
 - [6] B. P. Stojković et al., Phys. Rev. B **62**, 4353 (2000).
 - [7] M. Uehara et al., Nature **399**, 560 (1999).
 - [8] J. M. Tranquada et al., Phys. Rev. Lett. **73**, 1003 (1994).
 - [9] J. M. Tranquada et al., Phys. Rev. B **54**, 7489 (1996).
 - [10] M. A. Kastner et al., Rev. Mod. Phys. **70**, 897 (1998).
 - [11] H. A. Mook and F. Doğan, Nature **401**, 145 (1999); H. A. Mook et al., Nature **404**, 729 (2000).



FIG. 1. The angle α which describes the buckle in the copper (solid circle) - oxygen (open circle) - copper bonding.




FIG. 2. Illustration of the effect of tensile misfit strain on structure. The periodic potential has wavelength a , the lattice spacing set by the crystal, while the natural length of the shorter doped Cu-Cu bonds is $l_0 < a$. Due to the tensile misfit, the Cu atoms are unable to remain at the minima of the periodic potential and, at the same time, to conform to the natural length l_0 .

- [12] M. Arai et al., Phys. Rev. Lett. **83**, 608 (1999).
- [13] T. Timusk and B. Statt, Rep. Prog. Phys. **62**, 61 (1999).
- [14] R. J. McQueeney et al., Phys. Rev. Lett. **82**, 628 (1999).
- [15] A. Lanzara et al., Nature **412**, 510 (2001).
- [16] J. B. Goodenough, Ferroelectrics **130**, 77 (1992).
- [17] P. G. Radaelli et al., Phys. Rev. B **49**, 4163 (1994).
- [18] E. S. Bozin et al., Phys. Rev. Lett. **84**, 5856 (2000); *ibid* Phys. Rev. B **59**, 4445 (1999).
- [19] S. R. Shenoy et al., Phys. Rev. B **60**, R12537 (1999); K. O. Rasmussen et al. Phys. Rev. Lett. **87**, 055704 (2001).
- [20] M. F. Thorpe, J. Non-Crystalline Solids **57**, 355 (1983).
- [21] M. T. Dove et al., in *Local Structure from Diffraction*, edited by S. J. L. Billinge and M. F. Thorpe, page 253, New York, 1998, Plenum.
- [22] T. Egami and D. Louca, J. Supercond. **13**, 247 (2000).
- [23] J. D. Axe et al., Phys. Rev. Lett. **62**, 2751 (1989).
- [24] S. R. White and D. J. Scalapino, Phys. Rev. Lett. **80**, 1272 (1998).
- [25] A. H. Castro-Neto Phys. Rev. B **64**, 104509 (2001).
- [26] C Castellani et al., Z. Phys. B **103**, 137 (1997).
- [27] A. Bussmann-Holder et al., J. Phys. Condens. Matter **13**, L169 (2001).
- [28] A. Bianconi et al., J. Phys. Condens. Matter **12**, 10655 (2000).
- [29] J. C. Phillips Phil. Mag. B **79**, 527 (1999).
- [30] V. J. Emery et al., Phys. Rev. Lett. **85**, 2160 (2000).
- [31] J. Zaanen et al., cond-mat/0102103 (2001).
- [32] G. Seibold et al., Phys. Rev. B **58**, 13506 (1998).
- [33] A. Bussmann-Holder, et al., Phil. Mag. B **80**, 1955 (2000).
- [34] P. Bak, Rep. Prog. Phys. **45**, 587 (1982).
- [35] A. M. Bratkovsky et al., Philos. Trans. Royal Soc. London A **354**, 2875 (1996).
- [36] O. L. Alerhand et al., Phys. Rev. Lett. **61**, 1973 (1988).
- [37] V. I. Marchenko, JETP Lett. **33**, 381 (1981).
- [38] Y. Frenkel and T. Kontovova, Zh. Eksp. Teor. Fiz. **8**, 1340 (1938).
- [39] B. Büchner et al., Phys. Rev. Lett. **73**, 1841 (1994).
- [40] B. Dabrowski et al., Phys. Rev. Lett. **76**, 1348 (1996).
- [41] S. J. L. Billinge et al., Phys. Rev. Lett. **72**, 2282 (1994).
- [42] J. P. Attfield et al., Nature **394**, 157 (1998).
- [43] J. Jung, preprint.
- [44] W. W. Schmahl et al., Phil. Mag. Lett. **60**, 241 (1989).

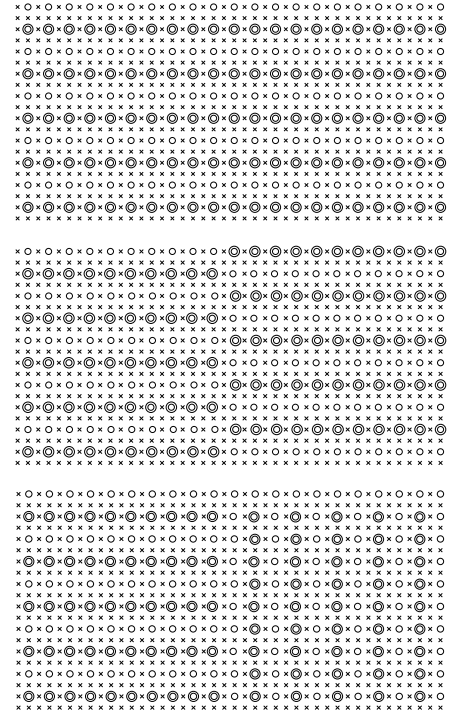


FIG. 3. Stripe nanostructures in cuprates. In systems with tensile misfit, the static stripe (top panel) has a high strain energy. Interleaved stripes (middle panel) and the weave microstructure (bottom panel) reduce this strain energy as they can accommodate strain relaxation. One unit cell of each microstructure is shown. Only copper atoms are shown. Concentric circles indicate doped sites, while sites indicated by crosses are excluded from the strain relaxation. For illustration purposes the natural length of bonds between doped sites are 10% shorter than bonds between undoped sites.